

Characterization of poly(vinyl chloride) powder produced by emulsion polymerization

Sevdiye Atakul Savrık · Devrim Balköse ·
Sevgi Ulutan · Semra Ülkü

IVMTT2009 Special Chapter
© Akadémiai Kiadó, Budapest, Hungary 2010

Abstract The effect of emulsion process formulation ingredients on the morphology, structure, and properties of polyvinyl chloride (PVC) powder has been considered in this study. PVC powder was extracted with ethanol and films were obtained by solvent casting from tetrahydrofuran. Characterization of powders, films, and ethanol extract was performed through FTIR spectroscopy, DSC, AFM, SEM, EDX analysis, methylene blue, and nitrogen adsorption. PVC powder was composed of spheres of a large particle size range from 10 nm to 20 μm as shown by SEM. The specific surface area of the PVC powder was determined as 16 and 12 $\text{m}^2 \text{g}^{-1}$ from methylene blue adsorption at 25 °C and from N_2 adsorption at -196°C , respectively. AFM indicated the surface roughness of the films obtained by pressing the particles was 25.9 nm. Density of PVC powder was determined by helium pycnometry as 1.39 g cm^{-3} . FTIR spectroscopy indicated that it contained carbonyl and carboxylate groups belonging to additives such as surface active agents, plasticizers, and antioxidants used in production of PVC. These additives were 1.6% in mass of PVC as determined by ethanol extraction. EDX analysis showed PVC particles surfaces were coated with carbon-rich materials. The coatings had plasticizer effect since, glass transition temperature was lower than 25 °C for PVC powder and it was 80 °C for ethanol extracted powders as found by using differential scanning calorimetry. These additives from polymerization

process made PVC powder more thermally stable as understood from Metrom PVC thermomat tests as well.

Keywords Poly(vinyl chloride) · Emulsion polymerization · Surface area · Density · Ethanol soluble additives

Introduction

Polyvinyl chloride (PVC) is a polymer which can be produced by bulk polymerization, suspension polymerization, and emulsion polymerization. PVC produced by emulsion polymerization is mainly used in producing flexible products such as artificial leather. PVC powder and plasticizers are mixed forming plastisols and by heating them plastigels are obtained. In emulsion polymerization water soluble initiators are applied and polymerization takes place either in the micelles or in water, where always exists a certain amount of solved vinyl chloride monomer (VCM). A typical recipe for emulsion polymerization is “Demineralized water 110–140 parts, Vinyl chloride 100 parts, Emulsifier 0.1–1 parts, Initiator 0.1–0.2 parts”. The initiator systems widely used in emulsion polymerization of vinyl chloride are potassium peroxosulfate–sodium bisulfate–copper or iron. One of the most important components of the emulsion polymerization recipe is the emulsifier. The quantity used has a major effect on the final latex particle size achieved, by determining the number of particles initiated. The nature of the emulsifier can also affect the number of particles initiated, particularly at low concentrations. Typical emulsifiers are the sodium salts of alkyl sulfates, alkyl sulfonates, alkylbenzenesulfonates, dialkyl sulfosuccinates, alkyl ethoxysulfates, fatty acid soaps, alkyl phenol ethoxylates, and fatty acid ethoxylates. The structure of the


S. A. Savrık · D. Balköse (✉) · S. Ülkü
Chemical Engineering Department, Izmir Institute
of Technology, 35430 Urla, Izmir, Turkey
e-mail: devrimbalkose@iyte.edu.tr

S. Ulutan
Chemical Engineering Department, Ege University,
35100 Bornova, Izmir, Turkey


particles (agglomerates) formed by removing the water is important in determining the final properties of the plastisol. For this reason a spray drier is normally employed to isolate the solid product. Dried agglomerates of primary PVC particles are collected by cyclone and bag-filter and then usually ground (milling) by pulverizer [1].

The emulsion PVC is used in plastisol production. Molecular mass, amount and type of emulsifier, mean particle size, and particle size distribution of PVC resin effect the rheology of PVC plastisols [2, 3].

PVC is dehydrochlorinated when heated during processing as shown by Eq. 1.

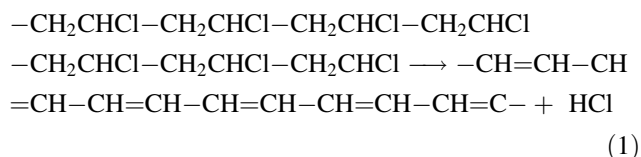

Heat stabilizers such as metal soaps, zeolites, antioxidants are added to PVC to prevent dehydrochlorination during processing. As an example substitution of a labile chlorine atom by a carboxylate group of a zinc soap according to Frye and Horst Mechanism is shown in Eq. 2 [4].



In this study characterization of an emulsion type PVC that was used in our previous research [5–9] on PVC thermal stabilization, PVC–silica composite preparation, biobased plasticizer testing was attempted to be made. For this purpose PVC was extracted with ethanol and films were prepared by solvent casting or dry pressing. Physical and chemical properties of the powders, films, and ethanol extracts were determined by advanced analytical methods.

Experimental

The PVC powder (PVC p), PETVINYL E38/74 from PETKIM was ethanol extracted for isolating additives from polymerization step. Five g PVC powder was extracted with 300 cm³ ethanol by using a Soxhlet extractor. The extracted powder was dried and called as ethanol extracted powder (EE PVC p). The ethanol phase was dried to obtain ethanol soluble additives. The extractions were done in duplicates to produce EE PVC p1 and EE PVC p2. The additives isolated with ethanol extraction, ethanol extracted PVC and PVC powder itself were attempted to be analyzed in this study. Films were prepared from PVC powder (PVC f), ethanol extracted PVC powder 1 (EE PVC f1), and ethanol extracted PVC powder 2 (EE PVC f2), by solvent casting from tetrahydrofuran.

Surface characterization of emulsion PVC powder was made by adsorption of methylene blue (MB) on PVC,

nitrogen adsorption, color test, density measurement, scanning electron microscopy (SEM), dispersive X-ray analysis (EDX), atomic force microscopy (AFM), energy, and Fourier transform infrared spectroscopy (FTIR).

2, 4, 6, 8, 10, 12, 14, 16, 18, and 20 mg dm⁻³ methylene blue solutions were prepared and 0.2 g of PVC powder was added to 100 cm³ of each solution. Adsorbed amount of methylene blue was determined after equilibration in dark at 298 K for 1 week period. Perkin Elmer UV–visible spectrophotometer was used for concentration measurements.

Nitrogen adsorption of PVC samples at 77 K was taken using micrometrics ASAP 2000.

SEM micrographs of gold coated PVC powder and were taken by a Phillips XL-30S FEG type scanning electron microscope. Chemical composition of the surface was determined by EDX analysis using the same instrument. MMSPM Nanoscope IV type instrument was used for AFM of the films obtained by pressing the PVC powder under 10 tons force. Quantachrome, Ultrapycnometer 1000 is used to determine the density of PVC powder. DSC analysis of PVC powders and ethanol extracts was done by heating the samples at 10 °C min⁻¹ rate up to 200 °C using Shimadzu DSC-50 differential scanning calorimeter. FTIR spectra of PVC powder, ethanol extracted powder, and PVC film prepared from tetrahydrofuran by solvent casting were obtained by Shimadzu FTIR 8210 spectrophotometer. Thermal stability of the PVC samples was tested with Methrom 763 PVC Thermomat apparatus.

Results and discussion

Morphology of powders

Emulsion PVC powders were spherical in shape and small particles are agglomerated on the surfaces of large particles as seen in Fig. 1. There are particles having diameter larger than 20 µm and as small as 10 nm.

AFM micrographs of surface of the films obtained by pressing the particles surface in Fig. 2 indicated fusion of the particles under pressure. The particle size of the particles was in the range of 100–500 nm. The surface roughness of the films obtained by pressing the particles was determined to be 26 nm.

Surface area

Methylene blue adsorption isotherm of the powders at 25 °C shown in Fig. 3 fitted to Langmuir adsorption model shown in Eq. 3 with a correlation coefficient of 0.98 and Langmuir constants Q_m and K_L were found as 6.18 mg g⁻¹ and 1.36 dm³ mg⁻¹, respectively. Assuming MB molecule covers an area of 1.38 nm² [10] on the surface, the specific

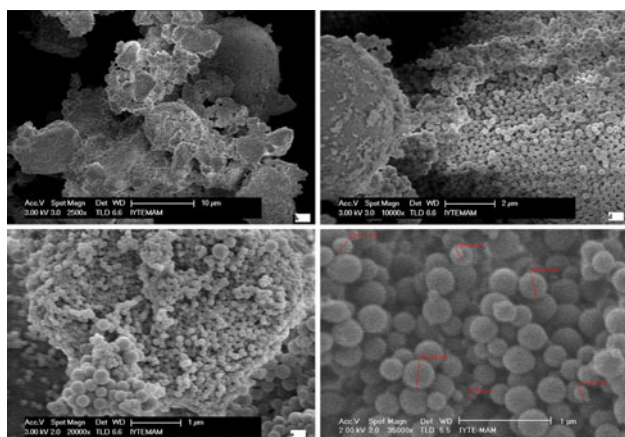


Fig. 1 Micrographs of PVC powder

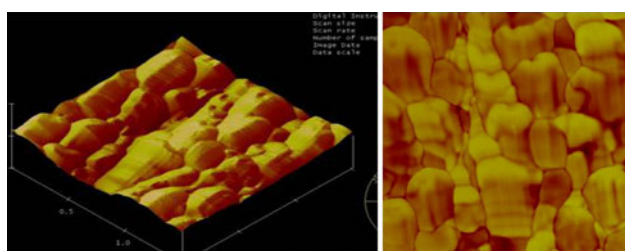


Fig. 2 Top view of PVC powder pellet; left side 3D and right side 2D, scale: 1.5 µm

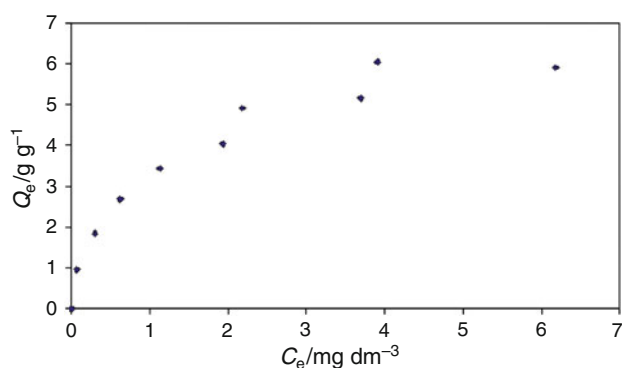


Fig. 3 Adsorption isotherm of methylene blue on PVC powder at 25 °C

surface area of the PVC powder was calculated as $16 \text{ m}^2 \text{ g}^{-1}$.

$$\frac{1}{Q_e} = \frac{1}{Q_m} + \frac{1}{K_L Q_m} \frac{1}{C_e} \quad (3)$$

where K_L = Langmuir constant (L mg^{-1}), Q_e = MB concentration at equilibrium in powder (mg g^{-1}), C_e = MB concentration at equilibrium in solution (mg L^{-1}), Q_m = MB concentration when monolayer forms onto particle surface (mg g^{-1}).

Nitrogen adsorption isotherm is plotted for volume adsorbed ($\text{cm}^3 \text{ g}^{-1}$) versus relative pressure and given in Fig. 4. While Langmuir model gives $12 \text{ m}^2 \text{ g}^{-1}$, BET model gives $8 \text{ m}^2 \text{ g}^{-1}$ surface area for nitrogen adsorption. The surface area values found from methylene blue and nitrogen adsorption are close to each other.

Density of PVC powder was determined by helium pycnometry and average density was 1.39 g cm^{-3} . Thus the specific volume of PVC powder, inverse of the density is $0.71 \text{ cm}^3 \text{ g}^{-1}$. Assuming adsorption occurring on the external surface of the spherical particles and using the surface area and volume of the particles average particle diameters were calculated as 264 and 300 nm from methylene blue and nitrogen adsorption, respectively.

Elemental composition of surfaces of powders (p) and films (f) on hydrogen free basis shown in Table 1, suggested that PVC particle surfaces were coated by the carbon-rich materials found in emulsion process additives. When the powders were extracted with ethanol the carbon content of the surface was decreased from 80 to 63% and 71% in mass for two parallel runs, respectively. The chlorine content of the powder surface (18%) was much lower than the expected theoretical value of (60%). When the powder was extracted with ethanol, chlorine content of the surface increased to 36 and 27% in mass for two parallel runs, respectively. When films were prepared from PVC powder/PVC p and PVC powder 1/PVC p1 extracted with ethanol an even distribution of carbon-rich material was obtained and the carbon/content was decreased to 59

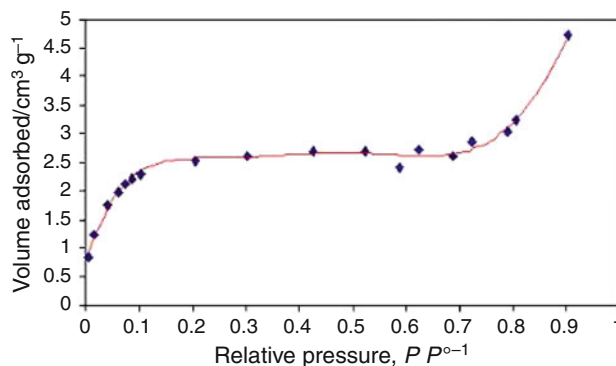


Fig. 4 Adsorption isotherm of nitrogen gas at -196°C

Table 1 Elemental composition of PVC surface on hydrogen free basis by EDX analyses, in Mass%

Element	Theoretical	PVC p	EE PVC p1	EE PVC p2	PVC f1	PVC f2
C	40	80	63	71	59	51
O	0	2	1	2	2	2
Cl	60	18	36	27	39	47